

# Experimental Investigation on Concrete by Replacement of Sand by Silica Sand and Artificial Sand

Vishal B. Swami

Student

Department of Civil Engineering

M.S. Bidwe Engineering College, Latur, India

Gundappa N. Shete

Professor

Department of Civil Engineering

M.S. Bidwe Engineering College, Latur, India

## Abstract

The use of alternative sand like silica sand, artificial sand is a natural step in solving part of depletion of natural aggregates. The experimental investigation on replacement of different material for concrete making started before half a century. Concrete made from silica sand and artificial sand as fine aggregate was studied for compressive strength, Split tensile strength and Flexural strength. So in this project, Silica sand and artificial sand had been used as replacement of fine aggregate by different percentage for making concrete of M-30 grade, with w/c ratio 0.42. The percentage replacement will be 0%, 10%, 20%, 30% with natural fine aggregates. For making concrete OPC cement is used. Cubes, beams and cylinders will be casted and tested compressive strength, Split tensile strength, and flexural strength. Optimum replacement of silica sand and artificial sand can be used in concrete for high compressive strength, Split tensile strength, and flexural strength.

**Keywords:** Silica Sand, Artificial Sand, Compressive Strength, Split Tensile Strength & Flexural Strength

## I. INTRODUCTION

In the world of construction, concrete like other materials is playing an important role in development. concrete is a composite material which is a mixture of cement, fine aggregate, coarse aggregate and water. The major constituents of which is natural aggregate such as gravel, sand, Alternatively, artificial aggregates, silica sand, fly ash may be used where appropriate. It possesses many advantages including low cost, general availability of raw material, adaptability, low energy requirement and utilization under different environmental conditions. The goal of sustainable construction is to reduce the environmental impact of a constructed facility over its lifetime. Concrete is the main material used in construction in the world. Industry is always trying to find new, better and economical material to manufacture new product, which is very beneficial to the industry. In the recent days, the various concrete develop and used in the construction, industrial and highway engineering. In this project we have used silica sand and artificial sand.

## II. MATERIALS

### A. Fine Aggregate (IS 2386 (Part- 1), (Part-3)):

#### 1) Sieve analysis of Fine aggregate:

The sieve analysis is conducted to determine the particle size distribution of fine aggregate. The different sieves sizes used for sieve analysis of fine aggregate was 4.75 mm, 2.36 mm, 1.18 mm, 600  $\mu$ m, 300  $\mu$ m, 150  $\mu$ m and 75 $\mu$ m. And test result is shown in the following table. Sand which is used for the construction purpose must be clean, free from waste stones and impurities.

Table - 2.1

Sieve analysis of fine aggregate

Sieve size (mm)	Weight retain (gms)	Cumulative weight retain (gms)	Cumulative percentage weight Retain (%)	Cumulative percentage weight passing
4.75	0	0	0	100
2.36	125	125	2.55	97.45
1.18	375	500	10.20	89.80
600 micron	1910	2410	49.14	50.86
300 micron	2294	4704	95.92	4.08
150 micron	200	4904	100.0	0.0

#### 2) Physical properties of fine aggregate:

Specific gravity of fine aggregate can be found out by Pycnometer and test result is tabulated in table and other physical properties also tabulated in following table.

Table - 2.2  
Physical properties of fine aggregate

Gradation	Fall in Zone III
Specific Gravity	2.63
Fineness Modulus	2.58
Water absorption	Nil

Table - 2.3  
Specific Gravity of fine aggregate

Sr no	Description	Value
1	Weight of pycnometer (W1) gms	643.83
2	Weight of pycnometer + soil (W2) gms	875
3	Weight of water + pycnometer + soil (W3) gms	1572
4	Weight of pycnometer + water (W4) gms	1450
5	Specific Gravity = -	2.63

**B. Silica sand (IS 2386 (Part-1), (Part-3)):**

1) Sieve analysis of Silica sand:

Silica sand is separated by different size of sieve. Sand size of 30 mesh to 80 mesh (500 micron) is used in the glass industries. Sand size 1.18mm to 600 micron can be used in making concrete mix as the partial replacement of fine aggregate

Table - 2.4  
Sieve analysis of silica sand

Sieve size (mm)	Weight retain (gms)	Cumulative weight retain (gms)	Cumulative percentage weight retain (%)	Cumulative percentage weight passing
4.75	0	0	0	100
2.36	35	3	0.7	99.3
1.18	365	400	8.1	91.9
600 micron	2115	2515	50.8	49.2
300 micron	2370	4885	98.6	1.4
150 micron	70	4955	100.0	0.0

2) Physical properties of silica sand:

Specific gravity of Silica sand can be find out by Pycnometer and test result is tabulated in table and other physical properties also tabulated in following table.

Table - 2.5  
Physical properties of silica sand

Specific Gravity	2.63
Fineness Modulus	2.58

Table - 2.6  
Specific Gravity of silica sand

Sr no	Description	Value
1	Weight of pycnometer (W1) gms	680
2	Weight of Water + soil (W2) gms	890
3	Weight of water + pycnometer + soil (W3) gms	1568
4	Weight of pycnometer + water (W4) gms	1445
5	Specific Gravity = -	2.63

**C. Artificial Sand:**

Artificial sand is a process controlled crushed fine aggregate produced from quarried stone by crushing or grinding and classification to obtain a controlled gradation product that completely passes the 4.75mm sieve. Artificial sand generally contain more angular particles with rough surface textures and flatter face than natural sand that are more rounded as a result of weathering. Over the time some investigations have shown that angular particles, rough surface of artificial sand influences the workability and finish ability in fresh concrete. The artificial sand have to satisfy the technical requisites such as workability, strength and durability of concrete and hence it has become necessary to study these properties in order to check the suitability and appropriate replacement level of artificial sand in comparison with the natural sand for producing concretes in an economical way

Table - 2.7  
Physical properties of Artificial sand

Specific Gravity	2.87
Fineness Modulus	2.58

**III. MIX DESIGN**

*Design stipulations*


Characteristics compressive strength required in the field at 28 days	30Mpa			
Maximum size of aggregate	10mm			
<i>Test data for materials</i>				
Cement	OPC 53 Grade			
Specific gravity of cement	3.15			
Compressive strength of cement at 7 days	satisfies the requirement of IS269-1989			
Specific gravity of coarse aggregate	2.68			
Specific gravity of Fine aggregate	2.63			
Type of exposure (assumed)	Mild			
Specific gravity of silica sand	2.63			
Specific gravity of artificial sand	2.87			
<i>Design procedure</i>				
<u>Step 1: Target mean strength of concrete</u>				
$f_{ck}^* = f_{ck} + tS$ where $f_{ck}$ -Characteristic compressive strength at 28 days=30 Mpa S-Standard deviation=4 (As per IS 456:2000) t-a statistical value depending on the risk factor=1.65 $f_{ck}^* = f_{ck} + tS$ $= 30 + 1.65 \times 4$ $f_{ck} = 36.6 \text{ Mpa}$				
<u>Step 2: Selection of water cement ratio</u>				
As per IS 456:2000 $w/c = 0.42$ (By strength) $w/c = 0.60$ (By durability) adopt lower w/c ratio				
<u>Step 3: Selection of water content</u>				
For 20mm size aggregate-water content including surface water per cubic meter of concrete=186 kg or 186 litres				
<u>Step 4: Determination of cement content</u>				
$w/c = 0.42$ $186/\text{cement} = 0.42$ Cement=443kg/m <sup>3</sup>				
<u>Step 5: Determination of fine aggregate</u>				
Given 2% air content by volume of concrete Applying equation, $V = [W + (C/S_c) + (1/p)(f_a/S_{fa})] / (1/1000)$ Where V-Absolute volume of fresh concrete which is equal to the gross volume(m <sup>3</sup> )minus the volume of entrapped air W-Water content(kg/m <sup>3</sup> ) of concrete C-Mass of cement kg/m <sup>3</sup> of concrete p-Ratio of fine aggregate (FA) to total aggregate by absolute volume f <sub>a</sub> -total mass of fine aggregate S <sub>fa</sub> -Specific gravity of fine aggregate V=Gross volume – Volume of entrapped air $= 1 - (2/100)$ $V = 0.98 \text{ m}^3$ $W = 186 \text{ kg/m}^3, C = 405 \text{ kg/m}^3, S_c = 3.15, p = 35\%, S_{fa} = 2.63$ $V = [W + (C/S_c) + (1/p)(f_a/S_{fa})] / (1/1000)$ $0.98 = [186 + (405/3.15) + (1/0.35)(f_a/2.63)] / (1/1000)$ F <sub>a</sub> = 559 kg/m <sup>3</sup>				
<u>Step 6: Determination of coarse aggregate content</u>				
$C_a = (1-p/p) f_a (S_{ca}/S_{fa})$ $C_a = (1-0.35/0.35) \times 613.053 \times (2.68/2.63)$ C <sub>a</sub> =1154 kg/m <sup>3</sup>				
<u>Step7: Mix proportion becomes</u>				
Table 3.12: Mix proportion				
	Water(Litres)	Cement(kg)	Fine aggregate(kg)	Coarse aggregate(kg)
	186	443	559	1154
	0.42	1	1.26	2.61

#### IV. RESULTS


For M 30 grade of concrete with W/C ratio of 0.42 mix was casted.. The cubes, beams were tested for compressive strength ,split tensile strength and flexural strength. These tested were carried out at age of 7 days and 28 days.

**D. Hardened Properties of Concrete:**

1) *Compressive strength test results:*

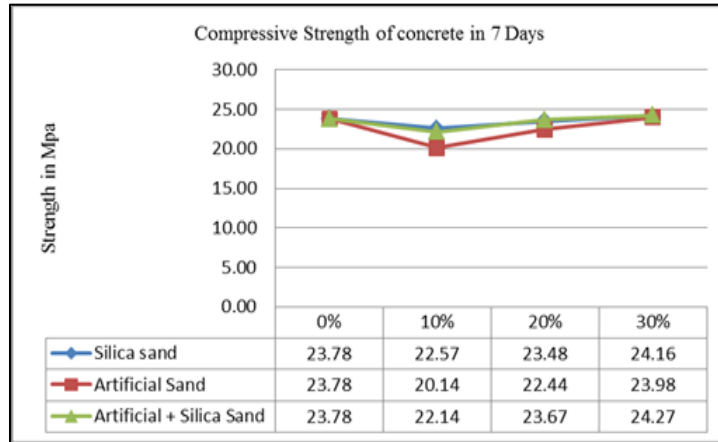


Graph 1: Compressive Strength of concrete for 7 Days

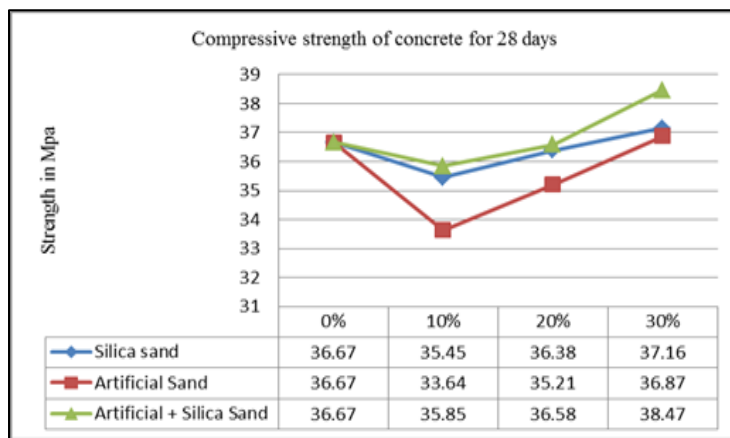


Graph 2: Compressive Strength of concrete for 28 Days

2) *Split - Tensile Strength test results:*

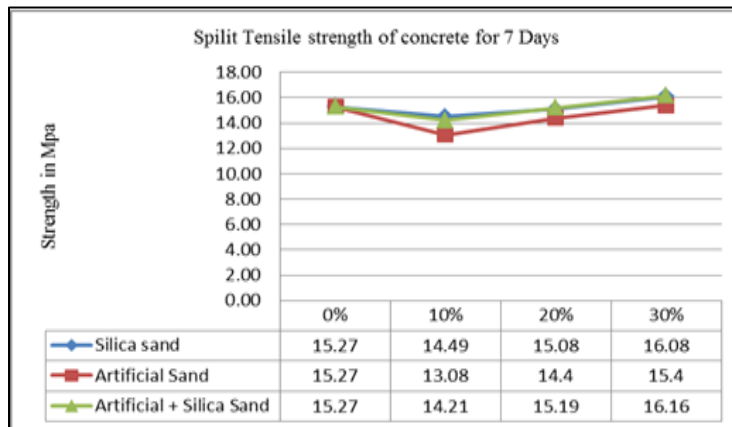


Graph 3: Split - Tensile Strength of concrete for 7 Days

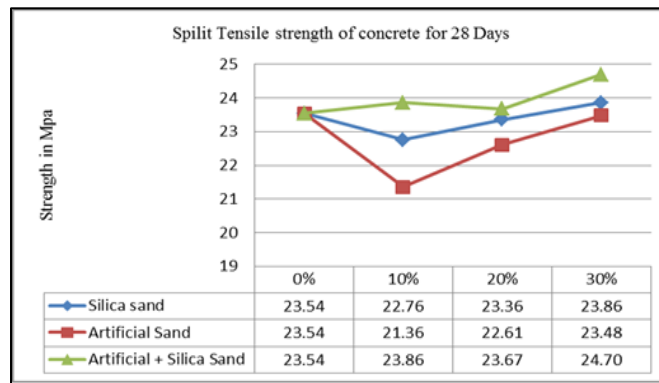


Graph 4: Split - Tensile Strength of concrete for 28 Days

3) Flexural Strength test results:

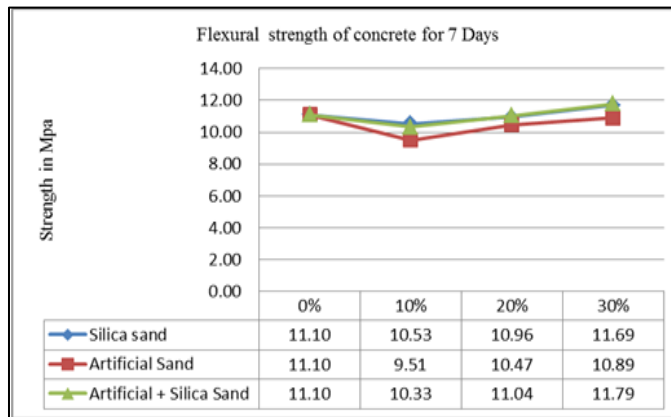

Graph 5: Flexural Strength of concrete for 7 Days

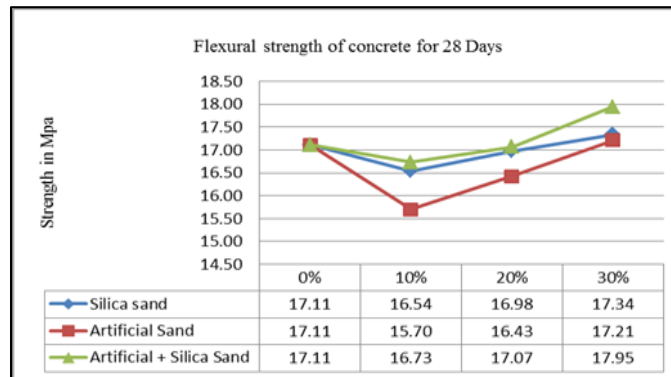

Graph 6: Flexural Strength of concrete for 28 Days

V. CONCLUSION

- 1) The compression test result indicates an increasing trend of compressive strength in the early age of the concrete specimens with 30 % silica sand. However, it shows that the strength of specimens was gradually increased up to 30% replacement of silica sand and artificial sand after 28 days. The target strength for M30 grade is 36.6 MPa that are achieved for all the specimens tested in the study.
- 2) The results also show that the concrete specimens with 30% replacement of Silica sand and artificial sand get the highest strength as compared to conventional concrete specimens with different percentage of silica sand, artificial sand. From the obtained result, it is possible to use 30% Silica sand and artificial sand for higher strength of concrete.
- 3) The Compressive Strength is increased by 1.05% for replacement of 30% Silica sand and 1.02% for replacement of 30% artificial sand and 1.09% for 30 % of Silica sand and artificial sand at 7 day.
- 4) The Compressive Strength is increased by 1.09% for replacement of 30% Silica sand and 1.05% for replacement of 30% artificial sand and 1.13% for 30 % of Silica sand and artificial sand at 28 day.

- 5) The Split tensile Strength is increased by 1.04% for replacement of 30% Silica sand and 1.01 % for replacement of 30% artificial sand and 1.09 % for 30 % of Silica sand and artificial sand at 7 days.
- 6) The Split tensile Strength is increased by 1.07% for replacement of 30% Silica sand and 1.05% for replacement of 30% artificial sand and 1.1% for 30 % of Silica sand and artificial sand at 28 days.
- 7) The flexural strength of beam is increased by 1.22% for 30% of Silica sand and 1.14% for 30% of and 1.45% for 30% Silica sand and artificial sand at 7 days.
- 8) The flexural strength of beam is increased by 1.35% for 30% of Silica sand and 1.20% for 30% of and 1.58% for 30% Silica sand and artificial sand at 28 days.
- 9) The Physical and Chemical properties of Silica sand and artificial sand are satisfied the requirement of code provisions. The other strength and durability test conducted shows that the Silica sand and artificial sand is fit to be used in concrete mix.

#### REFERENCES

- [1] Kerai Jignesh "Effect of use of silica sand as Fine material"
- [2] P. Aggarwal, Y. Aggarwal, S.M.Gupta, "Effect of bottom ash as replacement of fine aggregates in concrete" Asian journal of civil engineering, V. 8, 2007, Pg. No. 49 to 62
- [3] L. Evangelista, J. de Brito, "Mechanical properties of concrete made with fine recycled concrete aggregates". Cement and concrete composites, 2007, Pg. No. 397 to 401
- [4] Rafat Siddique, Geert de Schutter, Albert Noumowe, "Effect of used foundry sand on the mechanical properties of concrete", Construction and building materials, 2009, Pg. No. 976 to 980.
- [5] Farid Debieb, Said Kenai, "The use of coarse and fine crushed bricks as aggregate in concrete" Construction and building materials, 2008, Pg. No. 886 to 893
- [6] Joseph O. Ukpata, Maurice E. Ephraim, Godwin A. Akeke, "Compressive strength of concrete using lateritic sand and quarry dust as fine aggregate" APRN journal of engineering and Applied science, 2012, Pg. No. 81 to 92.
- [7] Malek K. Batayneh, Iqbal Marie, Ibrahim Asi, "Promoting the use of crumb rubber concrete in developing countries" Waste management, 2008, Pg. No. 2171 to 2176.
- [8] M. Shahul Hameed, A. S. S. Sekar, "Properties of green concrete containing quarry rock dust and marble sludge powder as fine aggregate" APRN journal of engineering and Applied science, 2009, Pg. No. 83 to 89.
- [9] Khalifa S. Al-Jabri, Makoto Hisada, Salem K. Al-Oraimi, Abdullah H. Al-Saidy, "Copper slag as sand replacement for high performance concrete" Cement and concrete composites, 2009, Pg. No. 483 to 488
- [10] Bahar Demirel, "The effect of the using waste marble dust as fine sand on the mechanical properties of the concrete" International Journal of the physical science, V.5(9), 2010, Pg. No. 1372 to 1380
- [11] Eun-Ik Yang, Myung-Yu Kim, Hae-Geun Park, Seong-Tae Yi, "Effect of partial replacement of sand with dry oyster shell on the long-term performance of concrete" Construction and building materials, 2010, Pg. No. 758 to 765
- [12] Zainab Z. Ismail, Enas A. Al-Hashmi, "Recycling of waste glass as a partial replacement for fine aggregate in concrete" Waste management, 2009, Pg. No. 655 to 659.
- [13] N. P. Rajamane, J. Annie Peter, P. S. Ambily, "Prediction of compressive strength of concrete with fly ash as sand replacement material" Cement and concrete composites, 2007, Pg. No. 218 to 223 A. Osunade, "Effect of replacement of lateritic soils with granite fines on the compressive and tensile strengths of laterized concrete" Building and environment, 2002, Pg. No. 491 to 496